



Structural Characterization and Luminescence Properties of $\text{Ca}_2\text{MgSi}_2\text{O}_7$ (CMS) Phosphor

Shashank. Sharma^{a,}, Sanjay Kumar Dubey^a, Sanjay Pandey^b, A.K. Diwakar^a*

^aDept. of Physics, Kalinga University, Naya Raipur, Chhattisgarh, 492101, India

^bDept. of Physics, Bhilai Institute of Technology, Raipur, Chhattisgarh, 492101, India

ABSTRACT

$\text{Ca}_2\text{MgSi}_2\text{O}_7$ (CMS) white light emitting phosphor was synthesized via traditional solid-state reaction technique. In order to find out the phase purity and crystal structure, characterization of the prepared powder samples was done by X-ray diffraction (XRD) technique. The results of the XRD studies obtained for this phosphor revealed its tetragonal, akermanite structure with a space group $P-421m$. It is observed that the XRD pattern matched well with JCPDS file No. 77-1149. The actual formation and functional group identification of phosphor was confirmed by Fourier transform infrared spectroscopy. Emission spectra have been obtained in blue region at 462nm wavelength with very poor PL intensity. The average crystallite size (D) is calculated as 26.33nm and lattice strain as 0.29. In this research paper, the XRD, FTIR and Photoluminescence (PL) properties of this phosphor are also reported.

Keywords: Photoluminescence (PL), XRD, FTIR, $\text{Ca}_2\text{MgSi}_2\text{O}_7$ (CMS), Akermanite, Solid-State Reaction.

1. Introduction

Silicate phosphors have broadly revolutionized research in the remarkable area of material science. Especially, in the area of LEDs and lightening markets. Mellite are a large group of compounds characterized through the general structure formula $\text{M}_2\text{T}^1\text{T}^2\text{O}_7$, [where M= Barium (Ba), Strontium (Sr), Calcium (Ca); T^1 = Magnesium (Mg), Zinc (Zn), Copper (Cu), Manganese (Mn), Cobalt (Co); T^2 = Germanium (Ge), Silicon (Si)], have been extensively investigated in the form of optical materials [1]. When compared with Alkaline earth silicates, sulfide phosphorescent phosphors and strontium aluminate phosphors. So, it was considered as appropriate hosts with high chemical stability and water-resistant property also discussed [2, 3]. Calcium magnesium silicate (CMS) has been broadly explored in the form of a host for long-lasting phosphor and plasma display panels [4]. Recently, in some literatures, long lasting alkaline earth silicate phosphors prepared via high temperature traditional solid reaction technique were reported [5, 6]. Akermanite, it belongs to the family of soro-silicates. The di calcium magnesium di silicate is also called as a host for long-lasting phosphors, generally activated with various RE ions, such as (Eu^{2+} , Nd^{3+} , Dy^{3+} or Mn^{2+}). This CMS phosphor has been extensively discussed in biological and medical areas of applications [7]. Silicate with akermanite structure may be a possible and attractive bio ceramics for tissue engineering applications [8]. In this study, $\text{Ca}_2\text{MgSi}_2\text{O}_7$ (CMS) phosphor was prepared via conventional solid-state reaction method. The structural characterization such as XRD, FTIR and optical properties like Photoluminescence characteristics were discussed in detail.

2. Experimental Study

* Corresponding author. Tel.: +917869544801.

E-mail address: dr.shashankeinstein@rediffmail.com

2.1 Material Preparation

The phosphor was synthesized via traditional solid-state reaction method. All the starting materials employed in the experiment are of analytical grade. Initially, all raw materials CaCO_3 (99.99%), MgO (99.99%), $\text{SiO}_2 \cdot \text{H}_2\text{O}$ (99.99%), and H_3BO_3 (99.99%) of Hi-media were purchased and weighed after calculation. Very little amount of H_3BO_3 (Boric acid) was added as a flux. It was mandatory that the all raw materials were mixed homogeneously by using acetone (CH_3COCH_3) and grinded thoroughly for 2 hours using the agate mortar and pestle in clock wise direction. The grinded sample was transferred in an alumina crucible. Sample was kept in programmable muffle furnace and after subsequently fired at 1100°C for 3 hours. The heating as well as the cooling rate of the furnace were set at 5°C per minute. Final $\text{Ca}_2\text{MgSi}_2\text{O}_7$ phosphor (white powder) was obtained after additional grinding up to 1 hour. The resulting sample was restored in airtight bottle for characterization studies.

The chemical reaction process is given as follows:




Fig: 1 $\text{Ca}_2\text{MgSi}_2\text{O}_7$ Phosphor

2.2 Material Characterization

XRD of the crystalline structure, size and phase composition of the synthesized phosphor were noted with the help of Bruker D8 advance X-ray diffractometer with $\text{Cu-K}\alpha$ radiation having wavelength ($\lambda = 1.5406 \text{ \AA}$), at 40 kV, and 40 mA voltage and current values, respectively. Actual formation and Functional group identification of this phosphor was obtained through FTIR. An FTIR spectrum was recorded with the help of Bruker Alpha Fourier Transform Infra-red Spectroscopy [FTIR]. For investigating the functional groups (4000 to 1400 cm^{-1}) as well as the finger print area (1400 to 400 cm^{-1}) of synthesized phosphor through mixing the sample with potassium bromide (KBr AR grade) with pallet preparation. In photoluminescence spectra (PL), emission spectra were recorded by a spectro-fluorophotometer (SHIMADZU, RF-5301 PC) using a xenon lamp of power 150 watt as excitation source. All experiments were performed in identical conditions and it was observed that the results were reproducible. All measurements carried out at the room temperature.

3. Results and Discussion

3.1 X-Ray Diffraction (Xrd)

XRD patterns of $\text{Ca}_2\text{MgSi}_2\text{O}_7$ (CMS) phosphor as a host was synthesized via conventional solid-state reaction technique are shown in Fig. 2. It is recorded in the range (10° to 80°). The position and intensity of diffraction peaks of this phosphor is well matched with the standard (Joint Committee on Powder Diffraction Standard) (JCPDS) No. 77-1149 [9]. The phase formation of the prepared phosphor was also confirmed by XRD characterization. The standard $\text{Ca}_2\text{MgSi}_2\text{O}_7$ structure cell volume and lattice parameters are observed from data base code AMCSO 0008032 [10]. All parameters of this phosphor are shown in Table no. 1. The prepared phosphor showed akermanite-type structure which comes under the tetragonal type of crystallography with space group $P4_2/m$.

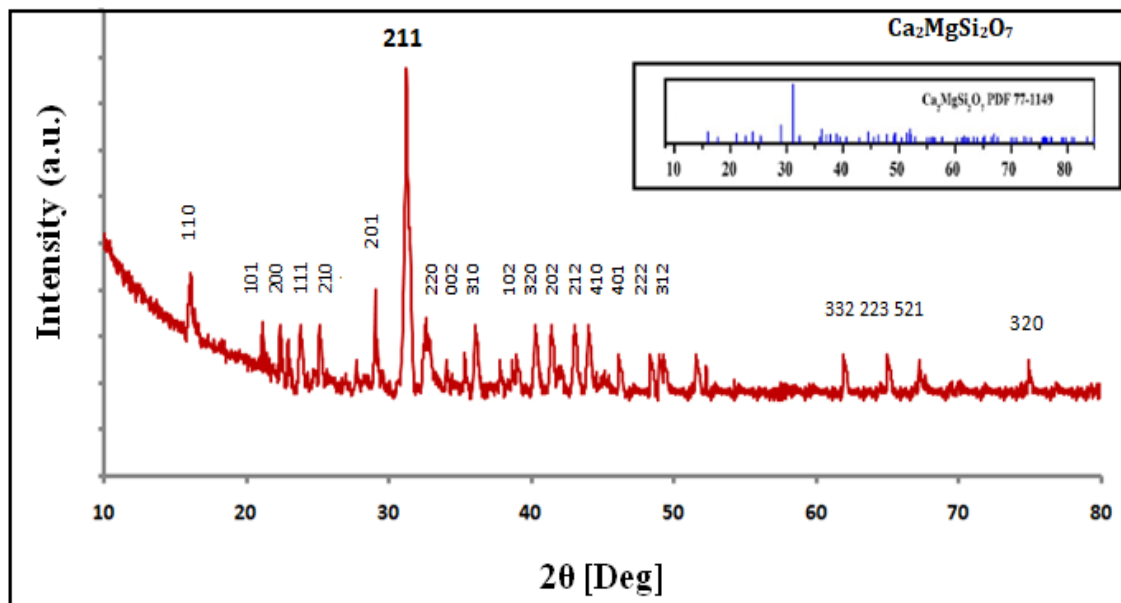


Fig: 2 XRD Pattern of $\text{Ca}_2\text{MgSi}_2\text{O}_7$ Phosphor

3.1.1 Debye–Scherrer Formula

For prominent peak (211), using Debye–Scherrer formula, the average crystallite size (D) of the $\text{Ca}_2\text{MgSi}_2\text{O}_7$ phosphor is calculated as (26.33) nm. Debye–Scherrer formula is represented as follows:

$$D = K\lambda / \beta \cos\theta \quad (2)$$

Where K is the Scherrer constant having value 0.94, λ is wavelength of incident X-ray ($\lambda = 1.5406 \text{ \AA}$), β = FWHM (Full Width Half Maximum) of the peaks and θ = corresponding Bragg's diffraction angle.

3.1.2 Strain Determination By Uniform Deformation Model (Udm)

The strain induced broadening in the powder material was calculated via the following formula given as below

$$\varepsilon = \beta / 4 \tan\theta \quad (3)$$

Table: (1) According to prominent peak (211), position of the peak of the XRD patterns and the calculation values of parameters.

NO	Parameters	$\text{Ca}_2\text{MgSi}_2\text{O}_7$ Phosphor
1.	Crystal Structure	Tetragonal
2.	Space Group	P^-421m
3.	Lattice Parameters	$a=b=7.8071 \text{ \AA}$ & $c= 4.9821 \text{ \AA}$ $\alpha=\beta=\gamma= 90^\circ$
4.	Crystalline Size D (nm)	26.33nm
5.	2θ (deg)	31.24
6.	Cell Volume	$303.663 (\text{ \AA})^3$
7.	Crystal plane Space	$2.86307 (\text{ \AA})$
8.	Strain	0.29

3.2 FTIR SPECTRA

3.2.1 KBr Pallet Preparation

The KBr pallet is displayed in fig. 3(a) and 3(b). Before recording the FTIR spectra of a synthesized sample, it is very essential to mix the synthesized sample with KBr (IR Grade) powder and grind it. After applying with hydraulic pressure to form a thin pallet. It is important to be note that KBr powder and sample should be in very little quantities. In this way, FTIR spectra and reading are obtained very clearly.



Fig: 3(a) Hydraulic Pressure Equipment, Fig: 3(b) KBr-BMS Pallet

3.2.2 Functional Group Characterization

The FTIR (Fourier Transform Infra-Red Spectroscopy) spectrum of this CMS phosphor has been showed in fig: 3(c). FTIR spectra were recorded in the range of (4000 cm^{-1} to 400 cm^{-1}). An intense band centred at 975.19 cm^{-1} and 945.35 cm^{-1} are allocated as a result of (Si-O-Si) asymmetric stretch, the band at 848.65 cm^{-1} is allocated to the (Si-O) symmetric stretch. Bands at 587.73 cm^{-1} , 483.54 cm^{-1} are allotted to the (Si-O-Si) vibrational mode. Furthermore, the absorption bands at 686.81 cm^{-1} , 645.28 cm^{-1} and 1360.68 cm^{-1} can be allocated to the existence of (SiO_4) group. The band centred at 1860.62 cm^{-1} can be ascribed to the existence of small quantity of the calcite [2]. The asymmetry stretching of carbonate (CO_3^{2-}) can be recorded in the range of $1900\text{-}1700\text{ cm}^{-1}$ [11] and its spectrum band at 1860.62 cm^{-1} are allotted to the (CO_3^{2-}) and band at 1639.46 cm^{-1} is as a result of to the vibration in Mg^{2+} ions. Likewise bending of sharp peaks situated in the region of 848.65 cm^{-1} , 723.58 cm^{-1} are allocated to the vibration in the Ca^{2+} ions [12]. The band centred at 3428.40 cm^{-1} which displays stretching vibration of (O-H) group. The band at 483.54 cm^{-1} is allocated to the (Mg-O).

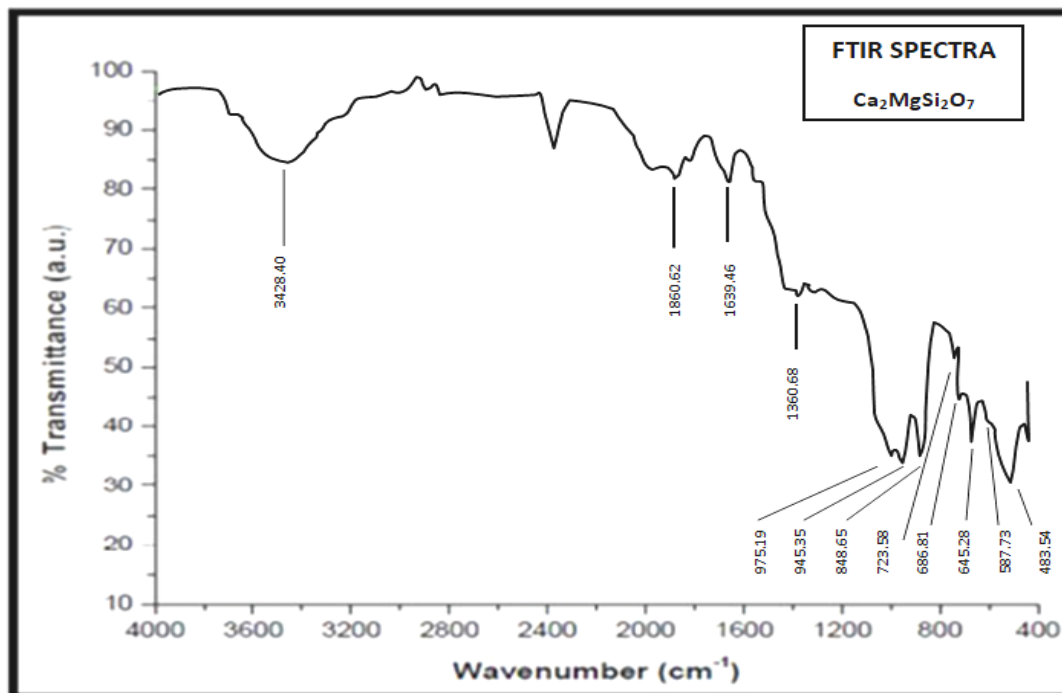


Fig: 3(c) FTIR Spectra of $\text{Ca}_2\text{MgSi}_2\text{O}_7$ (CMS) Phosphor

3.3 Photoluminescence (PL) Spectra

Fig. 4 showed the Emission spectra of host $\text{Ca}_2\text{MgSi}_2\text{O}_7$ phosphor. It is very clear that the Emission spectra have been obtained in blue region at 462nm wavelength with very poor PL intensity. Therefore, we have suggested that any phosphor as a host not displayed higher intensity in any wavelength, without any doping rare earth material.

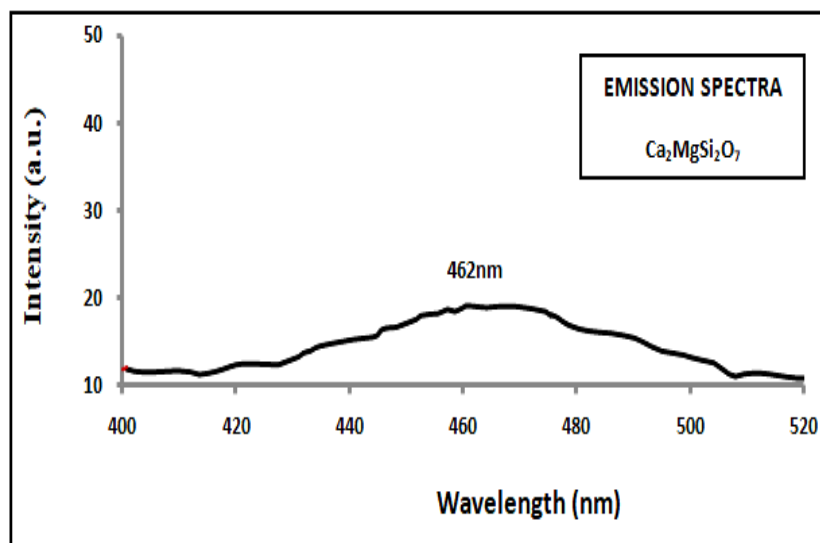


Fig: 4 Emission Spectra of $\text{Ca}_2\text{MgSi}_2\text{O}_7$ Phosphor

If we want to achieve higher intensity, then it will be mandatory to do rare earths doping with a host material with different concentrations. Due to which the PL intensity at various concentrations will be obtained in increasing order and at a certain concentration of rare earth, the PL intensity will be high.

Conclusion

In brief, $\text{Ca}_2\text{MgSi}_2\text{O}_7$ phosphor was successfully synthesized via traditional high temperature solid state reaction synthesis technique. The XRD spectra displayed that the standard pattern of the obtained phosphor was well matched through JCPDS file and lattice parameters were visualized with the data

base code AMCS0008032. The grain size and homogeneity of the phosphor is much better in the micro range. Actual formation of the phase structure of the CMS phosphor was determined via FTIR spectra. The CMS phosphor as a host showed the very poor PL emission intensity obtained in blue region at 462 nm wavelength. The phosphor is also applicable for the white light emitting diodes (WLEDs).

Acknowledgement

We gratefully acknowledge the kind support for the facility of XRD analysis Dept. of Metallurgical Engineering and FTIR analysis Dept. of physics, NIT Raipur (C.G.). Authors are also thankful to Mr. Suresh Dua and Mr. Sanjay Kumar Deshmukh NIT, Raipur (CG) India for their great co-operation at their center and Dept of physics, Pt. Ravishankar Shukla University, Raipur (C.G.) for providing us the facility of Photoluminescence analysis. We are also heartily grateful to Dept. of physics, Dr. Radha Bai, Govt. Navin Girls College Mathpara Raipur (C.G.), providing the facility of muffle furnace and other essential research equipments.

REFERENCE

- [1] Talwar, G. J., C. P. Joshi, S. V. Moharil, S. M. Dhopte, P. L. Muthal, and V. K. Kondawar, "Combustion Synthesis of $\text{Sr}_3\text{MgSi}_2\text{O}_8$: Eu^{2+} and $\text{Sr}_2\text{MgSi}_2\text{O}_7$: Eu^{2+} Phosphors", *Journal of Luminescence*, Vol. 129, Issue.11, pp.1239-1241, 2009.
- [2] Qin Fei, Chengkang Chang*, Dali Mao, "Luminescence properties of $\text{Sr}_2\text{MgSi}_2\text{O}_7$ and $\text{Ca}_2\text{MgSi}_2\text{O}_7$ long lasting phosphors activated by Eu^{2+} , Dy^{3+} ", *Journal of Alloys and Compounds*, Vol. 390, Issue. (1-2), pp.133-137, 2005.
- [3] K. Yamazaki, H. Nakabayashi, Y. Kotera, A. Ueno, "Fluorescence of Eu^{2+} - Activated Binary Alkaline Earth Silicate", *Journal of the Electrochemical Society*, Vol. 133, Issue. 3, pp. 657, 1986.
- [4] Pandey, D., Sharma, R., & Brahme, N., "Study of Optical Properties of Di Calcium- Magnesium Di Silicate Based Phosphors Doped Rare Earth Material", *International Journal of Advanced Research*, Vol. 4, Issue. 1, pp. 1639- 1646, 2016.
- [5] Lin, Yuanhua, Zhongtai Zhang, Zilong Tang, Xiaoxin Wang, Junying Zhang, and Zishan Zheng, "Preparation of a new long afterglow blue-emitting $\text{Sr}_2\text{MgSi}_2\text{O}_7$ -based photoluminescent phosphor", *Journal of materials science letters*, Vol. 20, Issue. 6, pp.1505-1506, 2001.
- [6] Lin, Yuanhua, Zhongtai Zhang, Zilong Tang, Xiaoxin Wang, Junying Zhang, and Zishan Zheng, "Luminescent properties of a new long afterglow Eu^{2+} and Dy^{3+} activated $\text{Ca}_3\text{MgSi}_2\text{O}_8$ phosphor." *Journal of the European Ceramic Society*, Vol. 21, Issue. 5, pp. 683-685, 2001.
- [7] Karacaoglu, Erkul, and Bekir Karasu, "Effect of Activators and Calcination on Luminescence Properties of Åkermanite type Phosphors", *Indian Journal of Chemistry*, Vol. 54A, pp. 1394-1401, 2015.
- [8] S. Sharma, S.K. Dubey, (2021). The Significant Properties of Silicate Based Luminescent Nanomaterials in Various Fields of Applications: A Review. *International Journal of Scientific Research in Physics and Applied Sciences*, 9(4), 37-41.
- [9] (Joint Committee on Powder Diffraction Standard) JCPDS file No. 77-1149.
- [10] Data Base Code AMCS0008032.
- [11] Vicentini, G., Zinner, L.B., Zukerman-Schpector, J. and Zinner, K., "Luminescence and structure of europium compounds", *Coordination Chemistry Reviews*, Vol. 196, Issue. 1, pp.353-382, 2000.
- [12] Chandrappa, G.T., Ghosh, S. and Patil, K.C., "Synthesis and Properties of Willemite, Zn_2SiO_4 , and $\text{M}^{2+}:\text{Zn}_2\text{SiO}_4$ (M= Co and Ni)", *Journal of Materials Synthesis and Processing*, Vol. 7, Issue. 5, pp.273-279, 1999.